

**Product code**

XVT-2237

**Product group**

Polyamide Folder-Gluer Belts

**Joining method**

Thermofix

**Contact**

Martin Nykl

**Edition date**

27/01/2021

**Status**

Option

**Important**

- Joining is also possible with other Habasit devices.
- Machine setting data should be derived from the relevant operating instructions.
- Read the operating instructions of the necessary tools carefully before making the first joint.
- All data are approximate values and defined under the following standard climatic conditions:
  - 23 °C/73 °F, 50% relative humidity (DIN 50005/ISO 554), working voltage 225-235 V / 105-115 V.
  - Any change of these data may require different temperature and/or time and/or pressure.
- For further support, please contact the Habasit company responsible for your location.

**Skiving**

Skiving device	AT-300/301
----------------	------------


**Settings**

Recommended joining angle	75°
Skiving angle (setting value)	3
Paper grit	50
Target skiving length	45-60 mm <i>1.8-2.4 inch</i>
Working length	85 mm
Feeding speed, advance	30
Feeding speed, return	50
Mode of skiving	1
Number of operations	1

## Application of adhesives


### Step 1

- > Apply a masking tape (paper type about 0.1 mm thick) to the surface ON EACH SIDE to increase pressure in polyamide zone.
- > Start in the transition area between top fabric and polyamide layer in direction to thinner wedge end.
- > Tape makes sure that the most critical part of the joint gets enough pressure.

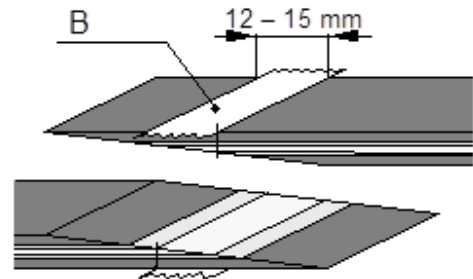

### Step 2

- > Mark off elastomer (friction cover) and polyamide areas (traction layer and intermediate fabric layers) with fine straight lines running parallel to the cutting edge (ball point pen or pencil).
- > Mark limit between Fixol and Vulcol always just within the area of pure polyamide fabric. Fixol does not stick elastomer.
- > Use spatula or brush. Coat evenly and THINLY indicated elastomer areas (friction cover) of BOTH skived surfaces with Vulcol (see sketch). Avoid applying Vulcol twice.
- > Allow to dry for about 10 min.
- > Use a natural bristle brush. Coat evenly and THINLY the indicated polyamide area (traction layer and one of both intermediate fabric layers) of BOTH skived surfaces with Fixol (see sketch).
- > Rub in with brush (on traction layer only) until Fixol becomes tacky.
- > Allow to dry for about 2 min.
- > The adhesives must exactly cover the prescribed surfaces. Put skived surfaces accurately on top of each other at the first attempt. Vulcol sticks on contact!
- > Close adhesive containers well.

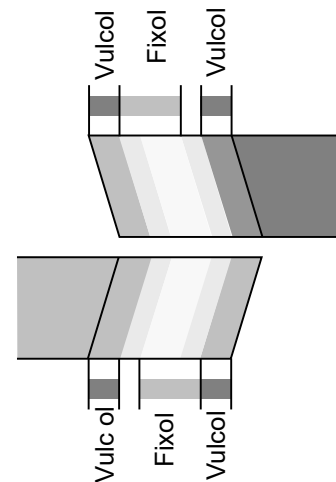




**Hot pressing**

Hot pressing device	PT-300
---------------------	--------

**Parameters**

Belt/Tape width range	0 - 300 mm 0 - 12 inch
Pressing temperature, bottom	120 °C 250 °F
Pressure setting	17 Nm
Pressing time	25 min
Cooling time in hot pressing device	10 min

**Inserts**

Top		
3		Pressure plate; top (with thickness equalizer)
2		Belt (conveying side up)
1		Heating plate; bottom (with set up plate)
Bottom		

Pressing remarks	Carry out a <b>QUALITY CHECK!</b> - Measure thickness over the joint area. In the center it must be: -0.05/+0.05 mm / -2/+2 thou. And over the whole area: -0.05/+0.10 mm / -2/+4 thou. According to experience, application requirements or customer recommendation the thickness of the joint area can deviate from above specification.
------------------	--

**Product liability**

This disclaimer is made by and on behalf of Habasit and its affiliated companies, directors, employees, agents and contractors (hereinafter collectively "HABASIT") with respect to the products referred to herein (the "Products"). SAFETY WARNINGS SHOULD BE READ CAREFULLY AND ANY RECOMMENDED SAFETY PRECAUTIONS BE FOLLOWED STRICTLY! Please refer to the Safety Warnings herein, in the Habasit catalogue as well as installation and operating manuals. All indications / information as to the application, use and performance of the Products are recommendations provided with due diligence and care, but no representations or warranties of any kind are made as to their completeness, accuracy or suitability for a particular purpose. The data provided herein are based on laboratory application with small-scale test equipment, running at standard conditions, and do not necessarily match product performance in industrial use. New knowledge and experience may lead to re-assessments and modifications within a short period of time and without prior notice.

EXCEPT AS EXPLICITLY WARRANTED BY HABASIT, WHICH WARRANTIES ARE EXCLUSIVE AND IN LIEU OF ALL OTHER WARRANTIES, EXPRESS OR IMPLIED, THE PRODUCTS ARE PROVIDED "AS IS". HABASIT DISCLAIMS ALL OTHER WARRANTIES, EITHER EXPRESS OR IMPLIED, INCLUDING, BUT NOT LIMITED TO, IMPLIED WARRANTIES OF MERCHANTABILITY, FITNESS FOR A PARTICULAR PURPOSE, NON-INFRINGEMENT, OR ARISING FROM A COURSE OF DEALING, USAGE, OR TRADE PRACTICE, ALL OF WHICH ARE HEREBY EXCLUDED TO THE EXTENT ALLOWED BY APPLICABLE LAW. BECAUSE CONDITIONS OF USE IN INDUSTRIAL APPLICATION ARE OUTSIDE OF HABASIT'S CONTROL, HABASIT DOES NOT ASSUME ANY LIABILITY CONCERNING THE SUITABILITY AND PROCESS ABILITY OF THE PRODUCTS, INCLUDING INDICATIONS ON PROCESS RESULTS AND OUTPUT.